


Calcium Silicate-Based Cements as Root Canal Medicament

This article was published in the following Dove Press journal:
Clinical, Cosmetic and Investigational Dentistry

Okba Mahmoud ^{1,2}
Walid Ali Al-Meer²
Mohideen Salihu Farook²
Nashwan Abdullah Al-Aff²

¹Department of Restorative Dentistry,
College of Dentistry, Ajman University,
Ajman, United Arab Emirates;

²Department of Restorative Dentistry,
Faculty of Dentistry, University of Malaya,
Kuala Lumpur 50603, Malaysia

Purpose: This study aims to retard the setting reaction of CSC by mixing it with 2% chlorhexidine gel (CHX) which will be used as an intracanal medicament, and to evaluate the removal of the experimental medicaments from the root canal.

Materials and Methods: White Portland cement, white ProRoot MTA and Biodentine were mixed with 2% CHX. The setting time, flowability and film thickness of the CSC/CHX mixture (experimental medicaments) were assessed and measured following the standards of ISO specification. Calcium ion release was measured using ICP-OES, while pH was tested using a pH meter. Moreover, twenty single-rooted teeth were filled with the experimental medicaments for seven days, then the medicaments were removed and the samples analyzed using SEM. Calcium hydroxide paste was used as a control.

Results: The setting time of the experimental medicaments was inhibited until 84 days. The calcium ion release of the experimental medicaments was significantly higher compared to the control over the period of 14 days ($P < 0.001$). The mean pH value was above 11.45 for all tested materials over a period of 14 days, with no significant difference between them ($P < 0.05$). There was no significant difference in film thickness of the experimental medicaments compared to the control ($P > 0.05$). However, the flowability of the experimental medicaments was significantly higher than the control ($P < 0.05$). SEM showed no significant differences in the removal of the intracanal medicaments between all the tested groups.

Conclusion: The addition of 2% CHX to CSCs retarded or inhibited its setting reaction over a period of 84 days. The calcium ion release and flowability of these experimental medicaments was found to be better than calcium hydroxide. Removal of the intracanal medicaments from the root canal was successfully achieved in all groups. Therefore, these experimental medicaments have the potential to be used as an enhanced root canal medicament.

Keywords: calcium silicate-based cements, chlorhexidine gel, intracanal medicament

Introduction

Mineral trioxide aggregate (MTA) is a calcium silicate-based cement (CSC) which launched into the dental field in the mid-1990s and it has gained much popularity since.^{1,2} MTA has been a material of choice for several endodontic procedures. It has been used to repair root defects such as perforations and internal and external resorptions.³ Furthermore, it has been successfully used as a root-end filling material during periapical surgeries and as an apical barrier for the open apex of the canals. More recently, it has been used as a root canal sealer and for treatment of dentine hypersensitivity.⁴⁻⁶ Additionally, MTA has been proposed to be used to stimulate a dentinogenic process in human pulp capping⁷ and obturation of retained primary

Correspondence: Okba Mahmoud
College of Dentistry, Ajman University,
Ajman, United Arab Emirates
Tel +971 67 056046
Fax + 971 67 438888
Email o.mahmoud@ajman.ac.ae

teeth.⁸ Furthermore, CSC has an antibacterial activity due to the release of hydroxide ions (OH⁻) by calcium silicate that triggers a rise in pH values.^{9,10}

In root canal treatment, the infected pulp tissues (a source of infection) are removed to eliminate or decrease pain through chemo-mechanical cleaning.¹¹ It has been shown that following chemo-mechanical preparation of the root canal system, bacteria can still be detected in the empty canals and that the bacteria may grow rapidly in between the dental appointments.¹² Shaping is usually not enough to complete the removal of bacteria; therefore, the combination of irrigation, instrumentation and intercanal medication is recommended.¹³ The antibacterial agent that is placed inside the canal, acting as an interappointment dressing to eliminate the residual bacteria and prevent further infection, is called intracanal medicament. It is used after shaping and cleaning the root canal to reduce periapical tissue inflammation and to achieve a root canal free of bacteria after instrumentation.¹⁴ Several intracanal medicaments such as calcium hydroxide, phenolics, aldehydes, halides, steroids, antibiotics and chlorhexidine are used in endodontics.^{15,16}

Among all the intracanal medicaments, calcium hydroxide is considered the gold standard.¹⁷ It is more often used as an interappointment dressing during root canal treatment because of its potential antibacterial actions in primarily infected root canals.¹⁸ However, it may fail to destroy certain facultative bacteria such as *Enterococcus faecalis* and *Candida albicans* found in secondary endodontic infections.¹⁹ Furthermore, its distribution through the whole canal is usually troublesome^{20,21} and its complete removal is problematic.²²

Although CSC has been used in different dental procedures as mentioned previously, it has not been used as intracanal medicament due to its setting reaction. To use CSC as a potential intracanal medicament for endodontic therapy, the setting reaction of the cement must be retarded or inhibited and antibacterial activity needs to be enhanced. Some investigators had replaced its mixing liquid with an antibacterial agent to enhance its antimicrobial properties. It should be noted that chlorhexidine has been used as endodontic irrigant and intracanal medicament during root canal treatment.²³ It has an antibacterial effect against *E. faecalis* which affects the endodontic success.²⁴ However, chlorhexidine does not act as a physical barrier against microbial recolonization and is ineffective in detoxifying bacterial endotoxins. Furthermore, it is not radiopaque if it is used as an intracanal medicament.²⁵ It is well established that the combination of 2% chlorhexidine liquid with MTA powder improves the antibacterial effect of

white and grey MTA against *E. faecalis*.²⁶ Another in vitro study concluded that a concentration of 2% chlorhexidine mixed with MTA powder had a larger zone of inhibition against *E. faecalis* compared to lesser concentrations.²⁷

The setting reaction of CSC can be interfered by inhibiting the process of hydration.²⁸ This can be achieved by substituting its mixing liquid with gel-based agents. A study performed by Kogan et al showed that the addition of chlorhexidine gel to MTA prevented the material from setting for four hours.²⁹

The purpose of this study is to retard the setting time and improve the handling characteristics of the CSC by mixing it with 2% chlorhexidine (CHX) gel and to determine the physical properties of this experimental medicament which is to be used as an intracanal medicament. Additionally, it aims to evaluate the removal of different experimental root canal medicaments and calcium hydroxide from the root canal using radiographs and scanning electron microscope (SEM).

Materials and Methods

Table 1 shows the composition and manufacture of each material used in the present study. Experimental medicaments used in this study are as follows:

- White Portland Cement (WPC) mixed with 2% chlorhexidine gel (CHX)
- White ProRoot MTA (WMTA) mixed with 2% chlorhexidine gel (CHX)
- Biodentine (BIO) mixed with 2% chlorhexidine gel (CHX)
- Calcium Hydroxide paste (CH paste)

The Physical Properties of the Intracanal Medicaments

Setting Time

Disc-shaped samples were prepared to assess the setting time of three CSC (n=5) namely: White Portland Cement (WPC), White ProRoot MTA (WMTA), and Biodentine (BIO) after mixing with 2% chlorhexidine gel (CHX). A custom made Perspex mold (Zectron Sdn Bhd, Kuala Lumpur, Malaysia) measuring 2mm in height and 10mm in diameter was used to prepare the disc-shaped samples. Experimental medicaments (a mixture of CSC and 2% CHX) was prepared by mixing the cement with the gel in the ratio of 2:1 (0.3g powder: 0.15g gel). The ratio of 2:1 was selected based on our preliminary study to have a

Table 1 Different Types of CSC and CHX Gel with the Control Used in This Study

Materials	Compositions	Manufacturer
1. White Portland Cement (WPC)	Tricalcium silicate, Dicalcium silicate, Tetracalciumaluminoferrite and Tricalciumaluminat.	Aalborg, Malaysia
2. Biodentine (BIO)	Powder: Tricalcium silicate, Dicalcium silicate, Calcium carbonate, Oxides and Zirconium oxide. Liquid: Iron oxide, calcium chloride and a water –soluble polymer.	Septodont, France
3. White ProRoot MTA (WMTA)	Tricalcium silicate, Dicalcium silicate, Tricalcium aluminate, Silicate oxide and Bismuth oxide.	Dentsply, USA
4. 2% Chlorhexidine Gluconate Gel (CHX gel)	Sorbitol, Aqua, PEG-40, Hydrogenated castor oil, Hydroxyethylcellulose, Panthenol, Cinnamal, Allantoin, Chlorhexidine Digluconate, Sodium Methylparaben, Sodium saccharin, PVM/MA copolymer, Citric acid.	Foramen, Spain
5. Calcium Hydroxide paste (CH paste)	Non-setting calcium hydroxide with barium sulfate.	Master-Dent, USA

medicament with workable consistency. Air entrapments inside the mixture were avoided by using mechanical vibration for 10 seconds to evenly distribute the mixture. Samples were then kept inside an incubator at 37°C, 100% humidity for 24 hrs until the test began.

The setting time was analyzed using the Vicat apparatus with a modified Gilmore needle based on the American Society for Testing and Materials C266-08 specifications and according to the ISO Standard 6876/2001 method.³⁰ During the test, the samples were subjected to a load of 456g. The final setting time for the specimens was taken as the time from mixing until the needle failed to make an observable indentation on the material. Samples were assessed for the following time periods: 1, 2, 3, 4, 5, 6, 7, 14, 28, 60 and 84 days.

pH and Calcium Ion Release Analysis

The pH and calcium ion tests were performed by filling polyethylene tubes 10 mm long and 1 mm in diameter with each tested material: WPC; WMTA; BIO that mixed with 2% CHX gel in the ratio of 2:1 (0.3g powder: 0.15g gel); and calcium CH paste which was used as a control group in this test. The CH paste group was mixed and prepared according to the manufacturer's recommendations. All samples were then stored in an incubator at 37°C, 100% humidity for 24 hrs until the analysis began.

For pH analysis of the tested materials (n=8), a digital pH meter (pH 700, Eutech, Thermo Fisher Scientific Inc, Waltham, USA) was used. The device was calibrated before each reading with buffer solutions at pH 4, 7, and 10. Fresh distilled water (5 mL) was added into the vial of each sample and allowed to equilibrate for 24 hrs in the

incubator before testing. Subsequently, the pH of the water surrounding the specimens was measured. After recording the readings, the sample was stored in the incubator until the next test. The replenishing of the distilled water into the vials was done one day prior to each of the following testing periods: 1, 7, 14, 21, and 28 days.

For calcium ion release of the tested materials (n=8), inductively coupled plasma-optical emission spectrometry (ICP-OES) (OPTIMA[®] 7000 DV, PerkinElmer, Inc., Waltham, USA) was used. The amount of 0.1g was measured from the stored samples and used for acid digestion and analysis. The acids used for the digestions were 67% concentrated nitric acid (HNO₃), 30% hydrogen peroxide (H₂O₂) and 37% concentrated hydrochloric acid (HCl). The digested sample was eventually analyzed for the following time periods: 1, 7, 14, 21, and 28 days. The method used to analyze the calcium ion release was based on the American Public Health Association 3120 (APHA) standard. The equipment was standardized using calibration standards and was set to blank before the readings.

Flowability and Film Thickness Analysis

Fresh samples of the same materials used in this study were mixed in the same manner to test the flowability and film thickness and then subjected to analysis. The control group (CH paste) was mixed and prepared according to the manufacturer's recommendations.

Flowability was analyzed based on ISO specification 6876/2001.³⁰ Two optically flat glass plates with a mass of 20 ± 2 g were used. An amount of 0.5 mL for each sample (n=5) was placed on the center of a glass plate using a 1mL

syringe. At 180 ±5 seconds after mixing, another plate was placed carefully on top of the mixed sample, followed by a load of 100g that was carefully applied onto the top surface of the plate. Ten minutes after mixing, the load was removed, and the major and minor diameters of the compressed discs were measured using a digital caliper with a resolution of ±0.01 µm (Absolute Digimatic 500–197, Mitutoyo Corp, Kawasaki, Japan). The mean of three such determinations for each sample was taken as the flow of the material.

Film thickness (n=5) was analyzed using two 5 mm thick optically flat glass plates with a contact surface area of 200 ±25 mm² that were positioned together, and their combined thickness was taken with a digital caliper (Absolute Digimatic 500–197, Mitutoyo Corp, Kawasaki, Japan) to an accuracy of ±0.01 µm. Freshly mixed samples were placed between the glass plates after 2 mins after the start of mixing, and a load of 150N was applied on the top surface of the glass plate for 10 mins according to the method described in ISO Standard 6876/2001.³⁰ The difference in thickness of the two glass plates with and without the sample was recorded as the film thickness of the material.

Removal the Intracanal Medicaments from the Root Canal

Teeth Selection

Twenty single-rooted human teeth with straight canals were used for this study. The teeth were examined visually for no visible root fractures, caries or cracks. The teeth were radiographed to confirm that they had a single canal without any internal calcifications, irregularities, and other anomalies and a completely formed root apex. The root surfaces were scaled with an ultrasonic instrument to remove any calculus or soft tissue from the surface, washed with distilled water and then stored in normal saline for two days.

The crown of the teeth was removed to obtain a standardized root length of 15 mm by using a diamond disc. The teeth were randomly divided into four experimental groups (n=5).

Root Canal Instrumentation

All root canals of the teeth were negotiated using K-files size 10 (Dentsply Maillefer) and a glide path was created using K files size 20. The working length was confirmed at 1 mm shorter than the apical foramen. Mechanical instrumentation of the root canal was performed using ProTaper Next rotary files (Dentsply Maillefer, Ballaigues, Switzerland) to size X3 by following the sequence prescribed by the manufacturer. The canals were irrigated with 5.2% NaOCl (Onemed,

Cairan Dental, Kuala Lumpur, Malaysia) and 17% EDTA paste (Vista Dental Products, South Street Racine, WI, USA) was used between each file during instrumentation. Patency of the root canals was verified by passing a K file size 10. Radiographs were taken for each tooth after completing the shaping and cleaning of the root canal.

Following irrigation with ultrasonic file size 25 (Irrisafe File, Satelec Acteon, Mendota Heights, MN, USA), the root canals were dried with X3 paper points. Experimental medicaments and the control were mixed using the same protocol used for evaluating the physical properties in this study. The root canals were filled with the medicaments using lentulo spiral size 25 (Dentsply Maillefer, Ballaigues, Switzerland) at a speed of 600 rpm. Radiographs were taken to confirm the complete filling and distribution of the medicament in the root canals. The access cavities were sealed with cotton pellets and temporary filling material (3M ESPE, CavitTM W, Germany). Teeth were incubated for 7 days in an incubator at 37°C temperature, 100% humidity (Memmert, Schwabach Germany).

Intracanal Medicament Removal

The intracanal medicaments in each group were removed using a combination of manual k-file size 15 and ultrasonic file size 25, together with irrigation solutions 5.25% NaOCl and finally irrigated by 17% EDTA solution. Radiographs were taken to ensure the complete removal of the intracanal medicaments from the root canal.

Root Splitting

The roots were grooved on the buccal and lingual aspects using a water-cooled cutflex diamond disc (DFS, Germany). The grooves were prepared short of the apical foramen by 0.5 mm, along the long axis of the root without touching the canal walls. All roots were split in the buccolingual direction using a chisel and mallet into two halves. Both halves of the root were marked at 12 mm (coronal third), 8 mm (middle third) and 4 mm (apical third) from the root apex for SEM evaluation. The method for splitting the teeth was adapted from previous studies.³¹

SEM Evaluation

Each Sample was dehydrated to reduce image noise thus facilitating the assessment of samples and minimizing artifacts. Therefore, all samples were placed in a desiccator for 24 hrs before SEM evaluation. Each sample was mounted on an aluminum stub. Then, images were viewed at 1000 times magnification and photographed at three different levels (apical, middle and coronal thirds, respectively).

Scoring and Calibration

A scoring procedure was defined to assess the quantity of residue on the canal walls. Two experienced endodontists (who were unaware of the experimental groups to which each section belonged) conducted the analysis using the following 5-grade scale:³¹

Score 1: 80%–100% removal of medicament (total cleanliness)

Score 2: 60%–80% removal of medicament (great cleanliness)

Score 3: 40%–60% removal of medicament (partial cleanliness)

Score 4: 20%–40% removal of medicament (light cleanliness)

Score 5: 0%–20% removal of medicament (no cleanliness)

Statistical Analysis

All data was statistically analyzed by using SPSS 20.0. One-way analysis of variance (ANOVA) with Tukey's post hoc test was used to analyze all the results for the tested materials for all the experiments. The significant level was set at $p < 0.05$ or $p < 0.001$.

For evaluation of intracanal medicament removal, scores for each sample were calculated, tabulated and analyzed with SPSS. Cohen's kappa coefficient was used to measure inter-rater reliability and indicated substantial agreement between two examiners. The Kruskal–Wallis test was used to determine differences between all groups. The significant level was set at $p < 0.05$.

Results

The Physical Properties of the Intracanal Medicaments

Setting Time

The setting time of experimental medicaments was consistent between groups. The three experimental medicaments

that mixed with 2% CHX gel did not set until the end of the testing period (1, 2, 3, 4, 5, 6, 7, 14, 28, 60, and 84 days).

pH Analysis

Throughout the experimental period, the results of pH measurements were alkaline. The mean pH values for all the experimental medicaments varied between 10.55–12.18 (Table 2). Analysis of variance (one-way ANOVA) showed a significant difference at all times of the study ($p \leq 0.001$) as shown in Table 3. However, BIO/CHX gel mixture showed the highest pH values among other experimental medicaments used in this study except for day 1. CH paste was significantly higher than other experimental medicaments used in this study during the testing periods ($p \leq 0.001$).

Calcium Ion Release

Analysis of variance (one-way ANOVA) showed a significant difference at all times of the study ($p \leq 0.001$) as

Table 3 Tukey HSD Post Hoc Test for pH Value

	(I) Group	(J) Groups	Mean Difference (I-J)	P value
Day 1	CH paste	WPC + CHX	0.71625*	$p \leq 0.001$
		Bio + CHX	0.90250*	$p \leq 0.001$
		MTA + CHX	1.22500*	$p \leq 0.001$
Day 7	CH paste	WPC + CHX	0.47125*	$p \leq 0.001$
		Bio + CHX	0.37375*	$p \leq 0.001$
		MTA + CHX	0.80500*	$p \leq 0.001$
Day 14	CH paste	WPC + CHX	0.48125*	$p \leq 0.001$
		Bio + CHX	0.20000*	$p \leq 0.001$
		MTA + CHX	0.77625*	$p \leq 0.001$
Day 21	CH paste	WPC + CHX	1.30000*	$p \leq 0.001$
		Bio + CHX	0.61375*	$p \leq 0.001$
		MTA + CHX	1.70125*	$p \leq 0.001$
Day 28	CH paste	WPC + CHX	0.44000*	$p \leq 0.001$
		Bio + CHX	0.18000*	$p \leq 0.001$
		MTA + CHX	0.51500*	$p \leq 0.001$

Note: *p value ($p \leq 0.001$) significant value.

Table 2 Mean and Standard Deviation of pH Value for the Experimental Medicaments and CH Paste Used in This Study Over 28 Days Period

Periods	WPC + 2% CHX Gel	BIO + 2% CHX Gel	WMTA + 2% CHX Gel	CH Paste	P value
Day 1	11.84±(0.027)	11.66±(0.028)	11.34±(0.029)	12.56±(0.029)	$p \leq 0.001$
Day 7	12.09±(0.025)	12.18±(0.028)	11.75±(0.035)	12.56±(0.027)	$p \leq 0.001$
Day 14	11.74±(0.026)	12.02±(0.027)	11.45±(0.029)	12.22±(0.039)	$p \leq 0.001$
Day 21	10.95±(0.029)	11.64±(0.028)	10.55±(0.037)	12.25±(0.029)	$p \leq 0.001$
Day 28	11.71±(0.027)	11.97±(0.037)	11.56±(0.202)	12.16±(0.035)	$p \leq 0.001$

Note: p value ($p \leq 0.001$) significant value.

Table 4 Mean and Standard Deviation of Calcium Ion Release (Mg/l) for the Experimental Medicaments and CH Paste Used in This Study Over 28 Days Period

Periods	WPC + 2% CHX gel (mg/l)	BIO + 2% CHX Gel (mg/l)	WMTA + 2% CHX Gel (mg/l)	CH Paste (mg/l)	P value
Day 1	1979.75±(06.32)	2460.25±(33.96)	1884.00±(52.48)	485.63±(03.15)	p≤0.001
Day 7	1926.25±(27.11)	2443.75±(35.38)	1845.00±(64.18)	494.63±(02.61)	p≤0.001
Day 14	1058.38±(25.90)	1898.62±(43.68)	1486.12±(33.430)	476.62±(02.82)	p≤0.001
Day 21	1050.00±(26.75)	1238.25±(07.166)	509.62±(46.356)	529.62±(03.37)	p≤0.001
Day 28	745.88±(28.68)	494.38±(21.567)	397.00±(28.005)	532.62±(03.37)	p≤0.001

Note: p value (p<0.001) significant value.

Table 5 Tukey HSD Post Hoc Test for Calcium Ion Release

	(I) Group	(J) Groups	Mean Difference (I-J)	P value
Day 1	CH paste	WPC + CHX	-1494.125*	p≤0.001
		Bio + CHX	-1974.625*	p≤0.001
		MTA + CHX	-1398.375*	p≤0.001
Day 7	CH paste	WPC + CHX	-1431.625*	p≤0.001
		Bio + CHX	-1949.125*	p≤0.001
		MTA + CHX	-1350.375*	p≤0.001
Day 14	CH paste	WPC + CHX	-581.750*	p≤0.001
		Bio + CHX	-1422.000*	p≤0.001
		MTA + CHX	-1009.500*	p≤0.001
Day 21	CH paste	WPC + CHX	-520.375*	p≤0.001
		Bio + CHX	-708.625*	p≤0.001
		MTA + CHX	20.000	0.463
Day 28	CH paste	WPC + CHX	-213.250*	p≤0.001
		Bio + CHX	38.250	0.012
		MTA + CHX	135.625*	p≤0.001

Note: *p value (p<0.001) significant value.

shown in Table 4. Tukey HSD Post hoc test (Table 5) showed that all the experimental medicaments used in this study released significantly higher calcium ions (mean values, mg/l) compared to CH paste until 14 days (p<0.001). Among the experimental medicaments, BIO/CHX mixture showed the highest calcium ions release at day 21 compared to CH paste (p<0.001). However, WPC/CHX mixture showed significantly higher calcium ions release compared to CH paste at day 28 (p<0.001).

Flowability

Analysis of variance (one-way ANOVA) showed a significant difference between the groups p<0.05, as shown in Table 6. Tukey HSD Post hoc testing showed a higher significant difference in the flowability between the experimental medicaments and CH paste (Table 7). All the

Table 6 Mean and Standard Deviation of Flowability (Mm) and Film Thickness (µm) for the Experimental Medicaments and CH Paste Used in This Study

Materials	Flowability (mm)	P value- One-Way ANOVA test	Film Thickness (µm)	P value- One-Way ANOVA test
WPC + 2% CHX gel	18.27±(1.79)	p≤0.05	0.10±(0.016)	0.844
BIO + 2% CHX gel	17.32±(1.80)		0.10±(0.031)	
MTA + 2% CHX gel	22.80±(1.00)		0.10±(0.019)	
CH paste	14.15±(0.52)		0.11±(0.016)	

Note: p value (p<0.05) significant value.

Table 7 Tukey HSD Post Hoc Test for Flowability

	(I) Groups	(J) Groups	Mean Difference (I-J)	P value
Flowability	CH paste	WPC + CHX	-4.11800*	0.001
		Bio + CHX	-3.17000*	0.011
		MTA + CHX	-8.65400*	p≤0.05

Note: *The mean difference is significant at the 0.05 level.

experimental medicaments except CH paste showed the flow to be greater than 17 mm, which complied with the ISO standards.^{30,32} It was demonstrated that the MTA/CHX mixture had significantly higher flowability than others.

Film Thickness

The results of the film thickness are shown in Table 6. In the present study, no statistically significant difference was presented in film thickness for the experimental medicaments compared to CH paste (p=0.844). Film thickness for all the experimental medicaments was 0.10 µm, while the

Clinical, Cosmetic and Investigational Dentistry downloaded from https://www.dovepress.com/ by 106.195.38.227 on 10-Aug-2021
For personal use only.

film thickness of CH paste was 0.11 μm , which is in agreement with the ISO standards.^{30,32}

Removal the Intracanal Medicaments from the Root Canal

The conventional radiograph showed that the intercanal medicaments were successfully removed from the root canal (Figure 1).

SEM for all the samples tested in this study showed a small amount of debris left in the root canal walls. Residue of intracanal medicaments was found in all experimental groups regardless of the material used in this study. Representative SEM micrographs are shown in Figure 2.

The Cohen's kappa coefficient of inter-rater reliability between the two examiners was 0.78 and there was high reproducibility with a significance level of $P=0.001$, while the intra-rater reliability scores were 94% and 96%.

The Kruskal–Wallis test showed that there was no significant difference between the four groups in terms of intracanal medicaments removal ($P=0.087$), as shown in Table 8 and Figure 2. Furthermore, the results revealed that there was no significant difference between the coronal third compared to the middle and apical thirds in all samples respectively. However, the mean of WPC (18.17) was less than CH (21.92), BIO (26.17), and WMTA (31.75). Thus, the removal of WPC from the root canal walls was superior compared to other intracanal medicaments used in this study.

Discussion

Mineral Trioxide Aggregate has been widely used in endodontics due to its good physicochemical properties and excellent biocompatibility.³³ Although MTA is preferred in many dental treatments due to its numerous advantages,³⁴ it has not been used as root canal medicament. This is because the removal of MTA from the root canal after being fully set and cured is extremely difficult.³³ This in vitro study explored the possibility of using calcium silicate-based cement (CSC) as an intracanal medicament by retarding its setting time. The experimental medicaments were a mixture of CSCs and 2% CHX. Furthermore, the physical properties such as setting time, pH, calcium ion release of the water surrounding the specimens, flowability and film thickness were analyzed. The application of intracanal medicament is a routine procedure throughout root canal treatment. Breaking the coronal seal could happen because the temporary restorations may dislodge or crack during treatment that may lead to contamination of the root canal. Therefore, using intracanal medicament is necessary to protect the root canal system during root canal treatment.^{35,36}

Several additives have been combined with MTA to enhance the working properties of the cement. It has been demonstrated that NaOCl gel may reduce the setting time and improve the handling characteristics of the mixture. It may also provide antimicrobial action. Additionally, chlorhexidine gluconate gel may retard and impair the setting time of the cement.²⁹ Researchers were using CHX in different concentrations and forms such as liquid, gel and powder with MTA to improve its antimicrobial properties.^{27,29,37} In a study

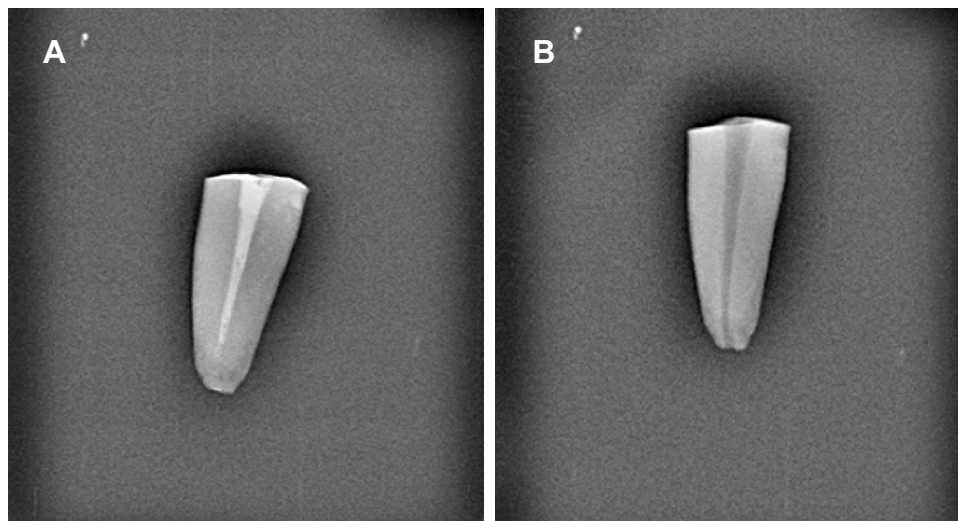


Figure 1 (A) Intracanal medicament placed into the canal after instrumentation and (B) after removal of intracanal medicament.

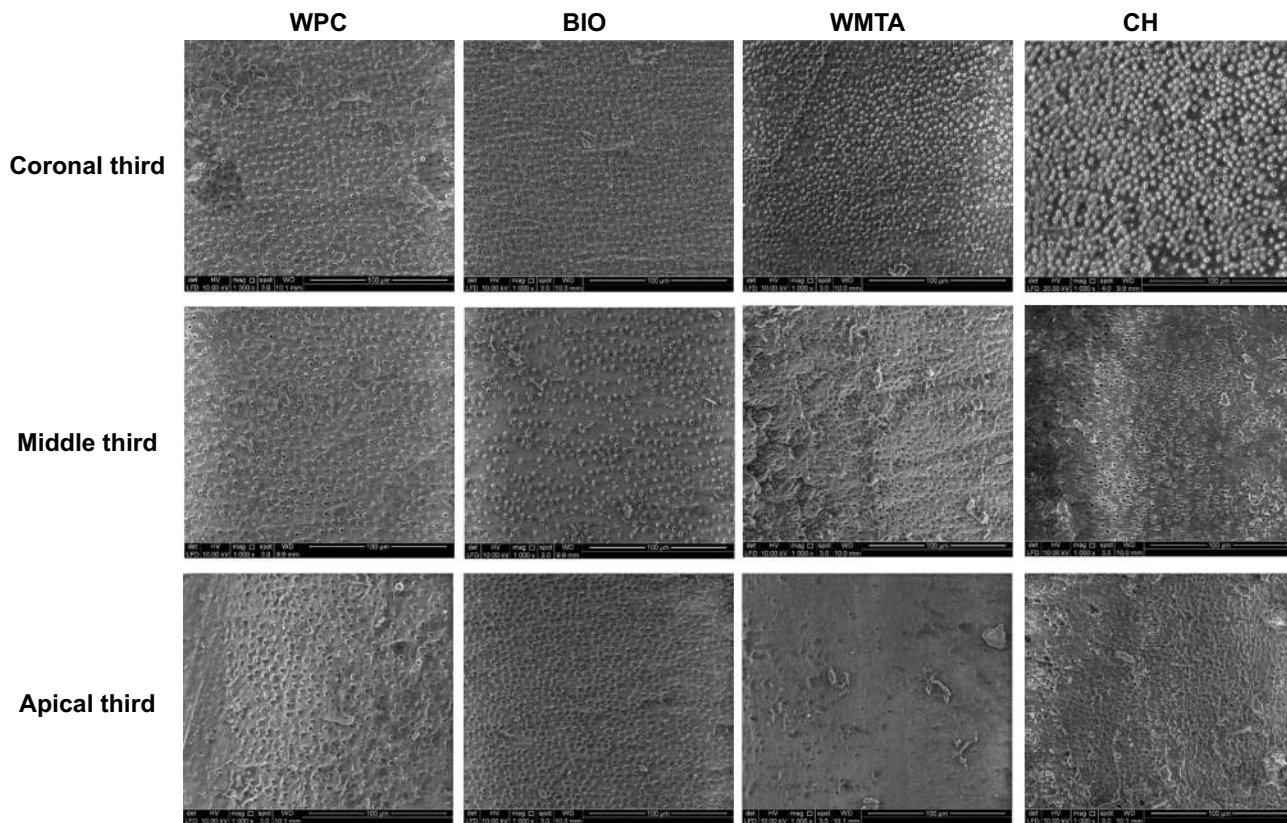


Figure 2 High power SEM (1000×) micrographs of a longitudinal section of the root canal retrieved from intracanal medicaments (WPC, BIO, WMTA and CH paste).

performed by Mittag et al²⁷ the antimicrobial properties of MTA were increased when mixed with CHX in a dose-dependent manner, whereas MTA with water had little antibacterial effect. Additionally, in an ex vivo study by Ramezani et al³⁸ mixing MTA with 0.12% CHX reduced the amount of bacterial leakage. The current study is the first which investigates the potential use of CSC mixing with 2% CHX gel as an intracanal medicament that could be used during inter appointment of root canal treatment. Delayed setting times is considered a problem and may limit the use of mineral trioxide aggregate (MTA) in endodontic procedures.²⁹ However, in this study, this limitation can be transformed into an advantage with the associated antibacterial efficacy of MTA, where the inhibition of the setting

time will add a new application for CSC and allow this material to be used as an intracanal medicament. Recently, MTA has become a common substitute for Ca(OH)₂, and the outcomes of the available clinical studies comparing MTA with Ca(OH)₂ indicate its superiority.³⁹

The setting time of MTA has been investigated extensively in previous studies. It has been reported that the final setting time of MTA is approximately 2 hrs and 45 mins.^{2,40} Another study reported 2 hrs and 55 mins for Grey MTA and 2 hrs and 20 mins for White MTA.⁴¹ In this study, the setting time of the experimental medicament (CSC/CHX mixture) was analyzed using a Gilmore needle and the procedure was based on the previous study which had determined the setting time of CSC.⁴² This study analyzed the setting time of experimental medicament for a period of 84 days. The results showed that 2% CHX gel prohibited the setting of all three cements until the end of the experimental period. This finding is in accordance with the study done by Kogan et al²⁹ however, they evaluated the setting time only for 4 hrs. Among the different experimental medicaments used in the study, Biodentine has faster setting time compared to others.⁴³ However, the addition of 2% CHX gel to CSC altered the ideal setting

Table 8 Difference in Intercanal Medicaments Removal Between the Different Groups Used in This Study Using SEM

	Materials	N	Mean	df	Sig ^a
Scores Measure	WPC + CHX	12	18.17	3	0.087
	BIO + CHX	12	26.17		
	WMTA + CHX	12	31.75		
	CH paste	12	21.92		
	Total	48			

Note: ^aNKruskal–Wallis Test.

time of the cement. Further research is needed to investigate the exact chemical reaction occurring in the experimental medicament.

Calcium ion release and an alkaline pH would stimulate tissue repair and provide an antimicrobial environment. It was also suggested that the material should have a pH of more than 7.0, along with calcium ion release to stimulate mineralization.⁴⁴ In this study, the release of calcium ions was assessed to check that CHX gel use does not interfere with the dissociation of calcium ions from experimental medicaments and also that it does not decrease pH values. Misra et al³⁵ studied the release of calcium ions and the pH of calcium hydroxide paste when mixed with different vehicles, and found that the calcium hydroxide with glycerine showed a highest calcium ion release followed by calcium hydroxide with chlorhexidine. The methodology used in this study to analyze the calcium ion release was similar to work done in the previous studies.^{45,46} All the materials analyzed presented the suitable release of calcium in the ICP-OES analysis. The experimental medicaments used in this study demonstrated a reduction in calcium ions over time and presented higher values at the initial period. The three experimental medicaments mixed with 2% CHX gel had an overall reduction in calcium ion release after 21 days, except for the WMTA/CHX gel mixture which showed lower calcium ion release than CH paste at 21 days, while CH paste was likely to be stable during all periods. This finding is similar to the results of other studies using the same analyzing equipment without using chlorhexidine.^{47,48} Among the group of experimental medicaments, BIO/CHX gel mixture showed the highest release of calcium ions over three weeks. The results of this study would suggest that the addition of 2% CHX gel to CSC has no inhibitory action on calcium ion release, thus corresponding with the results of previous studies.³⁷ The released calcium ions maximize alkalinizing activity and consequently increase the bactericidal effect of MTA.⁴⁹ It is interesting to note that the effective release of calcium ions for three weeks by all experimental medicaments tested in this study would be sufficient to allow their use as an intracanal medicament. This is based on the study by Sjögren et al⁵⁰ that demonstrated a one-week application of calcium hydroxide medicament is sufficient to reduce the bacterial load in the canal which was evident by negative culture.

In this study, CH paste showed the highest pH values compared to the experimental medicaments. Its pH was consistent until four weeks within a range of about 12.1–12.5. This is similar to the values mentioned in the literature.⁵¹ Among the different experimental medicaments used in this study, BIO/CHX gel mixture showed the

highest alkalizing activity until the end of the experiment. The current study demonstrated that all experimental medicaments had pH values of more than 10.5 until the end of the study. On the other hand, the WPC/CHX gel mixture and BIO/CHX gel mixture had a pH value of more than 11.5 until two weeks. It can be concluded that the pH values of these experimental medicaments may not be affected by the addition of CHX gel and could have bacteriostatic and bactericidal properties against *Enterococcus faecalis*. It is theorized that the high pH is responsible for the material's antimicrobial action and biological activity. This high pH is achieved because of the constant calcium release from MTA and Ca(OH)₂ formation.⁴⁹

Ideal intracanal medicaments should be easily applicable within the canal for proper contact within the canal walls and be able to be retrieved from the canal with minimal effort.⁵² Therefore, flowability and film thickness were assessed to achieve these objectives. This study showed that the flowability of the experimental medicaments was statistically significant compared to CH paste. The WMTA/CHX gel mixture had better flowability among the experimental medicaments used in this study. This could be due to differences in the particle size and shape of CSC. A few investigators have reported that MTA Angelus has finer and more homogeneous particle size compared to WPC and other types of MTA.^{53,54} One study reported that some particles of MTA have a diameter of less than 1.5 micrometers, which is smaller than the diameter of some dentinal tubules.²⁸ These studies were supporting the findings of this current study; however, the film thickness of the CH paste was similar to the experimental medicaments.

It has been emphasized that intracanal medication should be removed completely from the root canal because its presence on the dentinal wall can interfere negatively with the root canal obturation.⁵⁵ Thus, complete removal of the intracanal medication (calcium hydroxide) from the root canal before root canal obturation is necessary.⁵⁶ The effect of ultrasonic agitation of the irrigants has been evaluated and presented its efficacy in improving cleanliness and removing some calcium hydroxide from straight root canals.⁵⁷ However, complete removal of the calcium hydroxide from the root canal system could not be achieved.^{55–57}

Ultrasonic and rotary instrumentation without irrigates have been shown to be ineffective in the removal of set MTA from the root canal.⁵⁸ Similarly, in our study, the result of SEM showed that complete removal of intracanal

medications from the root canal walls could not be achieved. This could be attributed to the use of chlorhexidine which has the ability to decrease the surface microhardness of a partially set MTA,⁵⁹ and it is water-soluble and can be removed from the root canal by irrigation with distilled water.⁶⁰

Saghiri et al⁶¹ suggested that by decreasing the microhardness of MTA, the MTA can be removed more easily than hard and set cement. He demonstrated that a 37% hydrochloric acid (HCl) was an effective solution for the removal of MTA from the canal wall due to its ability to reduce microhardness of MTA. Therefore, the removal of CSC/CHX mixture from the root canal was easier than MTA because of the delay in the setting reaction of the cement. Regarding the calcium hydroxide paste, the vehicle used in its preparation plays an important role where the oil-based calcium hydroxide is more difficult to remove than powder form calcium hydroxide mixed with distilled water.⁶²

Conclusions

The addition of 2% CHX gel to CSC retarded or inhibited the setting reaction and significantly improved the calcium ion release and flowability of the experimental medicaments. The pH and film thickness of the experimental medicament were in acceptable range compared to CH paste. Among different experimental medicaments, BIO/CHX gel mixture showed superior physical properties compared to the others. Removal of the intracanal medicaments from the root canal was successfully achieved in all groups tested in this study. Based on the initial finding, these experimental medicaments have the potential to be used as an enhanced root canal medicament. Further research on this formulation (particularly biocompatibility and antibacterial activity) is needed.

Acknowledgment

This study was financially supported by the UMRG Grant (RG530-13HTM) and the PPP Grant (PG059-2014A) at the University of Malaya, Malaysia.

Author Contributions

All authors contributed to data analysis, drafting or revising the article, gave final approval of the version to be published, and agree to be accountable for all aspects of the work.

Disclosure

Financial support: A postgraduate research grant (PPP) from the Faculty of Dentistry, University of Malay (grant no. PS

169/2010B) was received by Okba Mahmood, Walid Ali Al-Meeri and Mohideen Salihu Farook. The authors report a patent Calcium Silicate-Based Cement (CSC) as Root Canal Medicament pending to PI2014703468. The authors report no other conflicts of interest in this work.

References

- Torabinejad M, Hong CU, Lee SJ, Monsef M, Ford T. Investigation of mineral trioxide aggregate for root-end filling in dogs. *J Endod.* 1995;21(12):603–608. doi:10.1016/S0099-2399(06)81112-X
- Torabinejad M, Hong C, McDonald F, Ford T. Physical and chemical properties of a new root-end filling material. *J Endod.* 1995;21(7):349–353. doi:10.1016/S0099-2399(06)80967-2
- Dawood AE, Parashos P, Wong RH, Reynolds EC, Manton DJ. Calcium silicate-based cements: composition, properties, and clinical applications. *J Investig Clin Dent.* 2015.
- Torabinejad M, Parirokh M, Dummer PMH. Mineral trioxide aggregate and other bioactive endodontic cements: an updated overview - part II: other clinical applications and complications. *Int Endod J.* 2018;51(3):284–317.
- Berkathullah M, Farook MS, Mahmoud O. The effectiveness of remineralizing agents on dentinal permeability. *Biomed Res Int.* 2018;2018:4072815. doi:10.1155/2018/4072815
- Jafari F, Jafari S. Composition and physicochemical properties of calcium silicate based sealers: a review article. *J Clin Exp Dent.* 2017;9(10):e1249–e1255. doi:10.4317/jced.54103
- Min K-S, Park H-J, Lee S-K, et al. Effect of mineral trioxide aggregate on dentin bridge formation and expression of dentin sialoprotein and heme oxygenase-1 in human dental pulp. *J Endod* 2008;34(6):666–670.
- O'sullivan SM, Hartwell G. Obturation of a retained primary mandibular second molar using mineral trioxide aggregate: a case report. *J Endod.* 2001;27(11):703–705. doi:10.1097/00004770-200111000-00013
- Chen Y-W, Hsu -T-T, Wang K, Shie M-Y. Preparation of the fast setting and degrading Ca–Si–Mg cement with both odontogenesis and angiogenesis differentiation of human periodontal ligament cells. *Mater Sci Eng.* 2016;60:374–383.
- Shie M-Y, Chiang W-H, Chen I-WP, Liu W-Y, Chen Y-WJMS, C E. Synergistic acceleration in the osteogenic and angiogenic differentiation of human mesenchymal stem cells by calcium silicate–graphene composites. *Mater Sci Eng C.* 2017;73:726–735. doi:10.1016/j.msec.2016.12.071
- Dall AQ, Jouhar R, Khoso NA. Comparison of inter-appointment pain between ledermix and no intracanal medicament in acute apical periodontitis. *JLUMHS.* 2011;10(03):106.
- Morrier JJ, Benay G, Hartmann C, Barsotti O. Antimicrobial activity of Ca(OH)₂ dental cements: an in vitro study. *J Endod.* 2003;29(1):51–54. doi:10.1097/00004770-200301000-00014
- Torabinejad M, Handysides R, Khademi AA, Bakland LK. Clinical implications of the smear layer in endodontics: a review. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod.* 2002;94(6):658–666. doi:10.1067/moe.2002.128962
- Chong B, Ford TP. The role of intracanal medication in root canal treatment. *Int Endod J.* 1992;25(2):97–106. doi:10.1111/j.1365-2591.1992.tb00743.x
- Barbosa CA, Goncalves RB, Siqueira JF, De Uzeda M. Evaluation of the antibacterial activities of calcium hydroxide, chlorhexidine, and camphorated paramonochlorophenol as intracanal medicament. A clinical and laboratory study. *J Endod.* 1997;23(5):297–300. doi:10.1016/S0099-2399(97)80409-8
- Gomes B, Souza S, Ferraz C, et al. Effectiveness of 2% chlorhexidine gel and calcium hydroxide against *Enterococcus faecalis* in bovine root dentine in vitro. *Int Endod J.* 2003;36(4):267–275.

17. Zehnder M, Söderling E, Salonen J, Waltimo T. Preliminary evaluation of bioactive glass S53P4 as an endodontic medication in vitro. *J Endod.* 2004;30(4):220–224. doi:10.1097/00004770-200404000-00009
18. Byström A, Claesson R, Sundqvist G. The antibacterial effect of camphorated paramonochlorophenol, camphorated phenol and calcium hydroxide in the treatment of infected root canals. *Dental Traumatol.* 1985;1(5):170–175. doi:10.1111/edt.1985.1.issue-5
19. Evans M, Davies J, Sundqvist G, Figdor D. Mechanisms involved in the resistance of *Enterococcus faecalis* to calcium hydroxide. *Int Endod J.* 2002;35(3):221–228. doi:10.1046/j.1365-2591.2002.00504.x
20. Lohbauer U, Gambarini G, Ebert J, Dasch W, Petschelt A. Calcium release and pH-characteristics of calcium hydroxide plus points. *Int Endod J.* 2005;38(10):683–689. doi:10.1111/j.1365-2591.2005.00972.x
21. Shetty S, Manjunath M, Tejaswi S. An in-vitro evaluation of the pH change through root dentin using different calcium hydroxide preparations as an intracanal medicament. *J Clin Diagn Res.* 2014;8(10):ZC13. doi:10.7860/JCDR/2014/6788.3956
22. Tandan M, Hegde MN, Hegde P. Effect of four different intracanal medicaments on the apical seal of the root canal system: a dye extraction study. *Indian J Dental Res.* 2014;25(5):607. doi:10.4103/0970-9290.147104
23. Basrani B. Chlorhexidine gluconate. *Aust Endod J.* 2005;31(2):48–52. doi:10.1111/aej.2005.31.issue-2
24. Delgado RJ, Gasparoto TH, Sipert CR, et al. Antimicrobial effects of calcium hydroxide and chlorhexidine on *Enterococcus faecalis*. *J Endod.* 2010;36(8):1389–1393. doi:10.1016/j.joen.2010.04.013
25. Gomes BP, Vianna ME, Zaia AA, Almeida JFA, Souza-Filho FJ, Ferraz CC. Chlorhexidine in endodontics. *Braz Dent J.* 2013;24(2):89–102. doi:10.1590/0103-6440201302188
26. Holt DM, Watts JD, Beeson TJ, Kirkpatrick TC, Rutledge RE. The anti-microbial effect against *enterococcus faecalis* and the compressive strength of two types of mineral trioxide aggregate mixed with sterile water or 2% chlorhexidine liquid. *J Endod.* 2007;33(7):844–847. doi:10.1016/j.joen.2007.04.006
27. Mittag S-G, Eißner C, Zabel L, Wrbas K-T, Kielbassa AM. The influence of Chlorhexidine on the antibacterial effects of MTA. *Quintessence Int (Berl).* 2012;43(10):901–6.
28. Camilleri J. Hydration mechanisms of mineral trioxide aggregate. *Int Endod J.* 2007;40(6):462–470. doi:10.1111/iej.2007.40.issue-6
29. Kogan P, He J, Glickman GN, Watanabe I. The effects of various additives on setting properties of MTA. *J Endod.* 2006;32(6):569–572. doi:10.1016/j.joen.2005.08.006
30. Standardization, I.O.f. and I.O.f. Standardization. *ISO 6876: Dental Root Canal Sealing Materials.* ISO Geneva; 2001.
31. Alturaiki S, Lamphon H, Edrees H, Ahlquist M. Efficacy of 3 different irrigation systems on removal of calcium hydroxide from the root canal: a scanning electron microscopic study. *J Endod.* 2015;41(1):97–101. doi:10.1016/j.joen.2014.07.033
32. ISO. *International Standards Organization in Dentistry—Root Canal Sealing Materials.* Switzerland: ISO; 2012.
33. Torabinejad M, Parirokh M. Mineral trioxide aggregate: a comprehensive literature review—part II: leakage and biocompatibility investigations. *J Endod.* 2010;36(2):190–202. doi:10.1016/j.joen.2009.09.010
34. Butt N, Talwar S, Chaudhry S, Nawal RR, Yadav S, Bali A. Comparison of physical and mechanical properties of mineral trioxide aggregate and biodentine. *Indian J Dent Res.* 2014;25(6):692.
35. Misra P, Bains R, Loomba K, et al. Measurement of pH and calcium ions release from different calcium hydroxide pastes at different intervals of time: atomic spectrophotometric analysis. *J Oral Biol Craniofacial Res.* 2017;7(1):36–41. doi:10.1016/j.jobcr.2016.04.001
36. Siqueira J Jr, Lopes HP. Mechanisms of antimicrobial activity of calcium hydroxide: a critical review. *Int Endod J.* 1999;32(5):361–369. doi:10.1046/j.1365-2591.1999.00275.x
37. Jacinto RC, Linhares-Farina G, Sposito ODS, Zanchi CH, Cenci MS. Influence of 2% chlorhexidine on pH, calcium release and setting time of a resinous MTA-based root-end filling material. *Braz Oral Res.* 2015;29(1):1–6. doi:10.1590/1807-3107BOR-2015.vol29.0036
38. Ramezani G, Savadkouhi ST, Sayahpour S, Dentistry C. The effect of chlorhexidine mixed with mineral trioxide aggregate on bacterial leakage of apical plug in simulated immature teeth using human fresh saliva. *J Int Soc Prev Community Dent.* 2017;7(5):247.
39. Bakland LK, Andreasen J. Will mineral trioxide aggregate replace calcium hydroxide in treating pulpal and periodontal healing complications subsequent to dental trauma? A review. *Dental Traumatol.* 2012;28(1):25–32. doi:10.1111/j.1600-9657.2011.01049.x
40. Uyanik O, Nagas E, Kucukkaya Eren S, Cehreli ZC, Vallittu PK, Lassila L. Effect of phytic acid on the setting times and tensile strengths of calcium silicate-based cements. *Aust Endod J.* 2019;45(2):241–245. doi:10.1111/aej.v45.2
41. Islam I, Chng HK, Yap A. Comparison of the physical and mechanical properties of MTA and Portland cement. *J Endod.* 2006;32(3):193–197. doi:10.1016/j.joen.2005.10.043
42. Bortoluzzi EA, Broon NJ, Bramante CM, Felipe WT, Tanomaru Filho M, Esberard RM. The influence of calcium chloride on the setting time, solubility, disintegration, and pH of mineral trioxide aggregate and white Portland cement with a radiopacifier. *J Endod.* 2009;35(4):550–554. doi:10.1016/j.joen.2008.12.018
43. Grech L, Mallia B, Camilleri J. Investigation of the physical properties of tricalcium silicate cement-based root-end filling materials. *Dental Materials.* 2013;29(2):e20–e28. doi:10.1016/j.dental.2012.11.007
44. Estrela C, Sydney GB, Bammann LL, Felipe O Jr. Mechanism of action of calcium and hydroxyl ions of calcium hydroxide on tissue and bacteria. *Braz Dent J.* 1995;6(2):85–90.
45. Carvalho CN, Freire LG, Carvalho APLD, Duarte MAH, Bauer J, Gavini G. Ions release and pH of calcium hydroxide-, chlorhexidine- and bioactive glass-based endodontic medicaments. *Braz Dent J.* 2016;27(3):325–331. doi:10.1590/0103-6440201600602
46. Natale L, Rodrigues M, Xavier T, Simões A, Souza D, Braga R. Ion release and mechanical properties of calcium silicate and calcium hydroxide materials used for pulp capping. *Int Endod J.* 2015;48(1):89–94. doi:10.1111/iej.2014.48.issue-1
47. Camilleri J. Characterization of hydration products of mineral trioxide aggregate. *Int Endod J.* 2008;41(5):408–417. doi:10.1111/j.1365-2591.2007.01370.x
48. Duarte MAH, de Oliveira Demarchi ACC, Yamashita JC, Kuga MC, de Campos Fraga S. pH and calcium ion release of 2 root-end filling materials. *Oral Surgery Oral Med Oral Pathol Oral Radiol Endodontol.* 2003;95(3):345–347. doi:10.1067/moe.2003.12
49. Duarte MAH, de Oliveira Demarchi ACC, Yamashita JC, Kuga MC, de Campos Fraga S. Oral medicine, oral pathology, oral radiology, and endodontology, *pH and calcium ion release of 2 root-end filling materials.* *Oral Surgery Oral Med Oral Pathol Oral Radiol Endod.* 2003;95(3):345–347. doi:10.1067/moe.2003.12
50. Sjögren U, Figdor D, Spångberg L, Sundqvist G. The antimicrobial effect of calcium hydroxide as a short-term intracanal dressing. *Int Endod J.* 1991;24(3):119–125. doi:10.1111/iej.1991.24.issue-3
51. Farhad A, Mohammadi Z. Calcium hydroxide: a review. *Int Dent J.* 2005;55(5):293–301. doi:10.1111/idj.2005.55.issue-5
52. Basrani B, Ghanem A, Tjäderhane L. Physical and chemical properties of chlorhexidine and calcium hydroxide-containing medications. *J Endod.* 2004;30(6):413–417. doi:10.1097/00004770-200406000-00009
53. Camilleri J, Montesin FE, Brady K, Sweeney R, Curtis RV, Ford TRP. The constitution of mineral trioxide aggregate. *Dental Materials.* 2005;21(4):297–303. doi:10.1016/j.dental.2004.05.010
54. Komabayashi T, Spångberg LS. Comparative analysis of the particle size and shape of commercially available mineral trioxide aggregates and Portland cement: a study with a flow particle image analyzer. *J Endod.* 2008;34(1):94–98. doi:10.1016/j.joen.2007.10.013

55. Vilela DD, Neto MM, Villela AM, Pithon M. Evaluation of interference of calcium hydroxide-based intracanal medication in filling root canal systems. *J Contemp Dent Pract.* 2011;12(5):368–371.
56. Jasrotia A, Farooq R, Bhagat RK, Bhagat K, Sharma N, Habib S. Removal efficacy of various calcium hydroxide/chlorhexidine medicaments from the root canal with the aid of biological microscope. *Ind J Dental Sci.* 2019;11(1):1.
57. Pabel A-K, Hülsmann MJO. Comparison of different techniques for removal of calcium hydroxide from straight root canals: an in vitro study. *Odontology.* 2017;105(4):453–459. doi:10.1007/s10266-017-0293-6
58. Boutsioukis C, Noula G, Lambrianidis T. Ex vivo study of the efficiency of two techniques for the removal of mineral trioxide aggregate used as a root canal filling material. *J Endod.* 2008;34(10):1239–1242. doi:10.1016/j.joen.2008.07.018
59. Butt N, Talwar S. In-vitro evaluation of various solvents for retrieval of mineral trioxide aggregate and their effect on microhardness of dentin. *J Conserv Dent.* 2013;16(3):199.
60. Ferraz CCR, de Almeida Gomes BPF, Zaia AA, Teixeira FB, de Souza-Filho FJ. In vitro assessment of the antimicrobial action and the mechanical ability of chlorhexidine gel as an endodontic irrigant. *J Endod.* 2001;27(7):452–455. doi:10.1097/00004770-200107000-00004
61. Saghiri MA, Garcia-Godoy F, Gutmann JL, et al. Removal of white mineral trioxide aggregate cement: a promising approach. *Biomed Res Int.* 2013;2013:1–7. doi:10.1155/2013/469164
62. Nandini S, Velmurugan N, Kandaswamy D. Removal efficiency of calcium hydroxide intracanal medicament with two calcium chelators: volumetric analysis using spiral CT, an in vitro study. *J Endod.* 2006;32(11):1097–1101. doi:10.1016/j.joen.2006.06.005

Clinical, Cosmetic and Investigational Dentistry

Dovepress

Publish your work in this journal

Clinical, Cosmetic and Investigational Dentistry is an international, peer-reviewed, open access, online journal focusing on the latest clinical and experimental research in dentistry with specific emphasis on cosmetic interventions. Innovative developments in dental materials, techniques and devices that improve outcomes and patient

satisfaction and preference will be highlighted. The manuscript management system is completely online and includes a very quick and fair peer-review system, which is all easy to use. Visit <http://www.dovepress.com/testimonials.php> to read real quotes from published authors.

Submit your manuscript here: <https://www.dovepress.com/clinical-cosmetic-and-investigational-dentistry-journal>